

Silk derived formulations for accelerated wound healing in diabetic mice

Muniba Tariq, Hafiz Muhammad Tahir, Samima Asad Butt, Shaukat Ali, Asma Bashir Ahmad, Chand Raza, Muhammad Summer, Ali Hassan and Junaid Nadeem

Department of Zoology, Government College University Lahore, Lahore, Pakistan

ABSTRACT

Background: The present study aimed to prepare effective silk derived formulations in combination with plant extract (*Aloe vera* gel) to speed up the wound healing process in diabetic mice.

Methods: Diabetes was induced in albino mice by using alloxan monohydrate. After successful induction of diabetes in mice, excision wounds were created via biopsy puncture (6 mm). Wound healing effect of silk sericin (5%) and silk fibroin (5%) individually and in combination with 5% *Aloe vera* gel was evaluated by determining the percent wound contraction, healing time and histological analysis.

Results: The results indicated that the best biocompatible silk combination was of 5% silk fibroin and 5% *Aloe vera* gel in which wounds were healed in 13 days with wound contraction: $98.33 \pm 0.80\%$. In contrast, the wound of the control group (polyfax) healed in 19 day shaving $98.5 \pm 0.67\%$ contraction. Histological analysis revealed that the wounds which were treated with silk formulations exhibited an increased growth of blood vessels, collagen fibers, and much reduced inflammation.

Conclusion: It can be concluded that a combination of *Bombyx mori* silk and *Aloe vera* gel is a natural biomaterial that can be utilized in wound dressings and to prepare more innovative silk based formulations for speedy recovery of chronic wounds.

Submitted 23 April 2020
Accepted 2 October 2020
Published 8 January 2021

Corresponding author
Shaukat Ali,
dr.shaukatali@gcu.edu.pk

Academic editor
Gwyn Gould

Additional Information and
Declarations can be found on
page 13

DOI 10.7717/peerj.10232

© Copyright
2021 Tariq et al.

Distributed under
Creative Commons CC-BY 4.0

OPEN ACCESS

Subjects Entomology, Zoology, Dermatology, Diabetes and Endocrinology, Drugs and Devices
Keywords Sericin, Fibroin, Silk, Diabetes, *Aloe vera*, Skin wound

INTRODUCTION

Cutaneous wound healing is a programmed, multifaceted and sequential biological process that relies on the interaction between a large number of cells and molecular factors to repair the barrier function of the skin (*Paquette & Falanga, 2002; Martínez-Mora et al., 2012*). A “wound” is the disruption of normal skin physiology, while “wound healing” is the process by which the body pursues to restore skin stability (*Sugihara et al., 2000*). Ideal healing of a skin wound requires synchronized incorporation of all molecular and biochemical events of cell proliferation, migration, deposition of extracellular matrix and remodeling (*Das & Baker, 2016*). However, this orderly advancement of the healing process is compromised in chronic, non-healing wounds (*Falanga, 2005*). Chronic wounds normally occur in diabetic patients due to their impaired wound healing process (*Spampinato et al., 2020; Farman et al., 2020*).

Diabetes is a prevalent health challenge that impacts people worldwide. It is recognized as a group of varied disorders with the common elements of glucose intolerance, hyperglycemia caused by insulin shortage, reduced efficacy of insulin action, or both (Alberti & Zimmet, 1998; Atlas, 2015). Non-healing chronic wounds are considered as one of the most serious complications of diabetes. Such complications are associated with an increased risk of bacterial infection, blood vessel and nerve injury, and ultimately amputation of limbs and other organs (Masood et al., 2019).

The wound healing process in diabetic patients is profoundly slow as compared to healthy individuals, hence prolonged healing duration increases the risk of wound associated infections (Menke et al., 2007; Dehghani et al., 2020). The current wound healing investigations signify the therapeutic potential of formulations in modulating the wound healing process and reducing suffering of patients (Nithya, Brinda & Anand, 2011). Scientists have tried different chemicals and herbal formulations to speed up wound healing in diabetic patients but there were certain limitations and the results were not much persuasive.

There is a long history of utilization of natural materials in the biomedical industry. Amongst many naturally occurring materials, silk obtained from silkworms is considered as an exceptional biomaterial which has a wide range of medical applications (Jastrzebska et al., 2015; Farokhi et al., 2018; Tahir et al., 2020; Elahi et al., 2020). It is classified as a 'model biomaterial' due to its remarkable mechanical strength (Vollrath & Porter, 2006; Tahir et al., 2019), impressive biocompatibility with skin tissues, negligible immunogenicity (MacIntosh et al., 2008) and minimal bacterial adhesion (Cassinelli et al., 2006). Mounting evidence of preclinical research demonstrates excellent wound healing properties of silk proteins since the 1990s (Shailendra & Das, 2019). Silk (particularly silkworm silk) started its journey in the biomedical industry when it was first used to suture skin wounds (Altman et al., 2003).

Silk is the strongest and most flexible naturally occurring fiber. It is smooth, shiny and soft in texture unlike most of the synthetic fibers (Altman et al., 2003). There are two proteins fibroin (80%) and sericin (20%) present in the silk thread which is secreted by *Bombyx mori*'s silk glands (Vepari & Kaplan, 2007; Kundu et al., 2014; Aramwit, Siritientong & Srichana, 2012; El-Fakharany et al., 2020). The middle and posterior silk glands of *B. mori* larvae produce a fibroin layer and three layers of sericin respectively (Zhou et al., 2000). Sericin and fibroin play an active role in accelerating wound healing (Li et al., 2020). The wound healing potential of sericin in cell culture and animal models is well reported (Aramwit & Sangcakul, 2007). Successful trials with fibroin based biomaterials, for example, sponges (Roh et al., 2006), hydrogels (Fini et al., 2005), films (Sugihara et al., 2000) and nanofibers mats (Schneider et al., 2009) have been conducted with impressive results. It has also been reported that silk based wound dressings stimulate cell proliferation and recruitment of cells such as keratinocytes in the wound bed to accelerate the wound healing process (Chouhan & Mandal, 2020). Scientists have prepared, silk fibroin/keratin-based biofilms to control the release rate of elastase enzyme in the chronic wound milieu (Roh et al., 2006; Vasconcelos et al., 2010).

As silk fibroin and sericin exhibit unique biological and physical properties, they are extensively explored by researchers in the biomedical industry for their utilization in wound healing materials. The current study attempts to evaluate the silk-based formulations in treating induced-skin wounds in diabetic mice model. The objectives of this study were to extract pure silk fibroin and silk sericin from silkworm cocoons and to prepare silk-based formulations in combination with plant extract that is, *Aloe vera* gel. Furthermore, in vivo wound healing potential of silk based formulations in artificially wounded diabetic mice model was also evaluated.

MATERIALS AND METHODS

Ethical statement

All animal trial techniques were directed as per local and worldwide controls. The nearby direction is the Wet op de dierproeven (Article 9) of Dutch Law (International) as detailed in our previous studies ([Ali et al., 2020a](#); [Ali et al., 2020b](#); [Hussain et al., 2020](#); [Ara et al., 2020](#); [Ali et al., 2019](#); [Khan et al., 2019](#); [Mumtaz et al., 2019](#); [Mughal et al., 2019](#); [Dar et al., 2019](#)) and The Institutional Bioethics Committee at Government College University Lahore, Pakistan (No. GCU/IIB/21 dated: 08-01-2019).

Rearing of mice in animal house

The Swiss albino mice weighing around 29–30 g and 8 weeks old were obtained from the Animal House, Department of Zoology, Government College University Lahore, Pakistan and used as experimental models. They were reared in standard plastic cages of length 10 inches, height 7 inches and width 5 inches in the same Animal House facility of Zoology Department, Government College University Lahore. Six mice were reared per cage under standard laboratory conditions (temperature 19–21 °C, humidity 45–65% and 12 hr light-dark cycle). They were fed standard animal diet and tap water in the cage. Mice were acclimatized for one week before the experimental procedures. The weight of each mouse was measured and noted throughout the experiment.

Diabetes induction

Alloxan and streptozotocin both are widely used diabetogenic agents, but alloxan was preferred over streptozotocin because it was easily available here at low cost. A single dose of alloxan monohydrate (CAT A7413-10G, Sigma-Alrich, Germany) was injected intraperitoneally to induce type 1 diabetes. The dosage of alloxan monohydrate was freshly prepared in saline solution at a dosage of 200 mg/kg body weight ([Ahmadi et al., 2012](#)). All animals were fed with glucose solution (10%) after receiving an injection of alloxan monohydrate to prevent them from sudden hypoglycemic state ([Vanitha & Karthikeyan, 2013](#); [Bouzghaya, Amri & Homblé, 2020](#)). After 24 h of induction of diabetes, blood samples were collected by pricking the tail tip of the mice. Blood glucose level was measured with an electronic glucometer (On-call extra blood glucose meter and test strips). Animals with a blood glucose level of ≥ 250 mg/dl were considered diabetic and were selected for further experimentation ([Chen et al., 2015](#)). Mice were given free access to food and water during the study and they were kept in standard plastic cages at room

temperature in the Animal House facility. Blood glucose levels of all albino mice were recorded before starting of the experiment. Only those mice that have normal blood glucose levels were used for further study and those having high blood glucose levels were excluded from the study ([Dra et al., 2019](#)).

Creation of skin excision wound in mice

Mice were randomly divided into six groups with each group consisting of 6 male mice. Animals were anesthetized intraperitoneally with ketamine (100 mg/kg) and Xylazine (10 mg/kg) in saline before wound induction. The dorsal fur of mice was shaved completely by using an electrical hand shaver. Two full thickness excision wounds were created on the dorsum of each mouse by using a 6mm biopsy punch device. These surgical interventions were carried out under sterile conditions. The total surgical time was 15–20 min for each mouse. All animals received their respective treatments once a day from post wounding day till complete healing. Body weight, skin color and skin irritation were observed and recorded daily.

Extraction of sericin from cocoons

Silk cocoons of *B. mori* (silkworm) were kindly supplied by the Sericulture section of Forestry department, Punjab, Pakistan. These cocoons were sliced into small pieces. For sericin extraction, 5 g of silk cocoon pieces were immersed in 100 ml of distilled water and autoclaved at 121 °C and 15 lb per square inch pressure for 1 hr. After 1hr the sericin solution was allowed to cool at room temperature and then filtered through a filter paper. The filtration process removed impurities from the sericin solution. The filtered sericin solution was subjected to lyophilizer (freeze drying) at –82 °C for 72 hr to obtain sericin powder ([Martínez et al., 2017](#)). Extraction procedures of sericin and fibroin were carried out separately by utilizing fresh silk cocoons each time.

Extraction of fibroin

Degumming

Silk cocoons synthesized by *B. mori* silkworms were soaked in warm water to loosen the threads. Silk threads from several cocoons were then unwound to obtain silk fibers. Raw silk fibers were then degummed in 0.5% NaHCO₃ at 100 °C for 1 hr rinsed thrice with distilled water and then dried overnight in oven (60–80 °C) ([Ju et al., 2016](#); [Tahir et al., 2020](#)).

Dissolution of silk fibers

Degummed silk (80 mg) was dissolved for 6–8 hr at 80 °C with constant stirring in a solvent system of calcium chloride: ethanol: distilled water in a molar ratio of 1:2:8 ([Wang & Zhang, 2013](#); [Yi et al., 2018](#)). Urea (8 mM) was also added to calcium chloride solvent to achieve 100% dissolution of silk fibers ([Min et al., 2004](#)).

Dialysis

After dissolution, the remnants of chemicals were removed through dialysis with a cellulose dialysis membrane in distilled water for 3 days. After dialysis the silk fibroin

solution was sonicated at 20 kHz: 400W for 1 hr and then lyophilized to obtain silk fibroin powder (Ha, Park & Hudson, 2003; Siavashani et al., 2020).

SEM analysis of silk fibroin and silk sericin

Powdered samples of silk fibroin and silk sericin were subjected to SEM (Scanning Electron Microscopy) (FEI NOVA 450 Nano SEM) (voltage 1000 kV) available at LUMS (Lahore University of Management Sciences). SEM analysis was done to estimate the approximate sizes of silk fibroin and sericin particles.

Extraction of *Aloe vera* gel

Fresh *Aloe vera* gel was extracted from the leaves of the plant. The pulp was scraped out from the leaves and blended into a smooth paste using a high-speed blender. The extracted gel was transferred into an airtight container and refrigerated (4 °C). This extraction was carried out under sterile conditions.

GC-MS analysis of *Aloe vera* gel

Aloe vera gel (5 ml) extracted from the leaves was analyzed by GC-MS (Gas chromatography-Mass spectrometry) on a GC-MS equipment at Department of Chemistry, GC University Lahore. GC-MS analysis was performed to detect the bioactive compounds present in the *Aloe vera* gel. The parameters used in GC-MS analysis were Retention time (RT), I Time, F Time, Area, Area%, Height, Height%, A/H and Base (m/z).

Preparation of formulations

Gel formulations were prepared for four treatment groups. There were two control groups that is, positive control in which wounds were treated with polyfax (Polyfax is a skin ointment with active ingredients Bacitracin zinc and Polymyxin B sulphate. Both of these ingredients are antibacterial. This ointment is used for the treatment of infected surgical cuts, burns, infected wounds, infected ulcers on skin etc) and negative control in which wounds were washed with saline solution (0.9%) daily. All the groups are shown below:

- T1 5% Sericin
- T2 5% Sericin and 5% *Aloe vera* gel
- T3 5% Fibroin
- T4 5% Fibroin and 5% *Aloe vera* gel
- C1 Positive control (Polyfax)
- C2 Negative control (Saline solution)

Sericin (5%)

The gel was prepared by dissolving 0.1g sodium carboxy-methyl-cellulose Na-CMC in distilled water to form a homogenous solution. Sericin solution (5%) was prepared in distilled water. Sericin solution was added to the Na-CMC solution with constant stirring until it became a homogenous gel (Ersel et al., 2016; Nishida et al., 2011).

Fibroin (5%)

Fibroin gel was also prepared by adopting the method outline above. Na-CMC (0.1 g) was dissolved in distilled water to form a homogeneous solution. The fibroin solution (5%) was

prepared in distilled water and added to the Na-CMC solution with constant stirring until the solution became thick and homogenous (Nishida et al., 2011).

Sericin (5%) and Aloe vera gel (5%)

Sericin solution (5%) was prepared in distilled water, mixed with 5% *Aloe vera* gel and vortexed for 1 min. The solution was stored in falcon tubes at low temperature (4 °C) to prevent the growth of microorganisms.

Fibroin (5%) and Aloe vera gel (5%)

Fibroin solution (5%) was prepared in distilled water and mixed with 5% *Aloe vera* gel. The solution was vortexed for 1 min and stored at low temperature (4 °C) in falcon tubes.

Application of gel formulations on wounds

The diabetic mice were subjected to their respective treatments till complete wound healing. The formulations were applied evenly on the wound surface daily.

Percent wound contraction

After wound creation, the wound margins were traced at 2 days interval on transparent graph paper. Measurements were continued until the complete (98–99%) wound restoration. After 2 days interval, the healed area was calculated. The contraction was represented as percent wound contraction and epithelialization time was observed after complete healing (Lodhi et al., 2016).

The rate of healing as percentage contraction was calculated using the formula:

$$= \frac{\text{Initial wound area} - \text{Wound area on a specific day}}{\text{Initial wound area}} \times 100$$

Histological evaluations

Skin sample of one mouse from each group was acquired at post wounding day 5 and 10. The central portion of tissue was fixed in 10% buffered formalin (pH = 7). Thin sections were prepared using a microtome and stained with hematoxylin-eosin and Masson's trichrome method. Wound healing effects were examined histologically under a light microscope using low power magnification (Aramwit & Sangcakul, 2007).

Euthanization and Dissection of animals

For euthanization, mice were placed in beakers and euthanized with a large piece of cotton soaked in chloroform. Beaker was covered properly with an aluminum foil. The mice were euthanized within 10–15 min. All euthanized mice were dissected and then skin samples were collected for histological evaluation.

Statistical evaluations

For statistical analysis, the normality of the data was assessed using Shapiro–Wilk's test. One-way ANOVA was conducted out to compare percent wound contraction in control and treatment groups, followed by Tukey's post-hoc test using SPSS software (version 20). All data were expressed as the mean ± SEM (Standard Error of Mean).

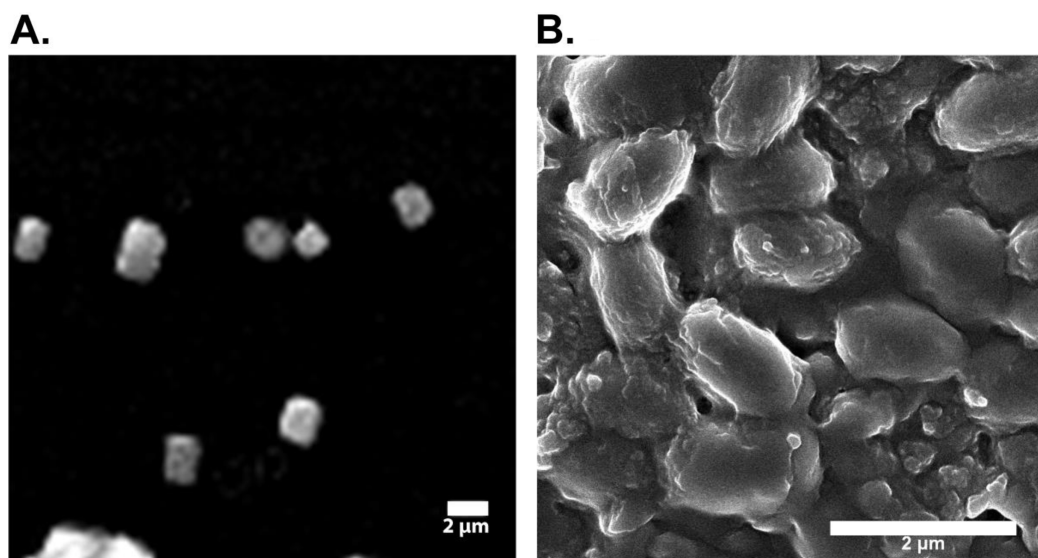


Figure 1 Electron micrographs of silk fibroin and sericin. (A) Electron micrograph of sonicated silk fibroin. (B) Electron micrographic image of silk sericin. [Full-size](#) DOI: [10.7717/peerj.10232/fig-1](https://doi.org/10.7717/peerj.10232/fig-1)

RESULTS

SEM analysis of silk fibroin and silk sericin

The scanning electron micrographs (SEM) showed 240–300 nm sized silk fibers of sonicated samples (Fig. 1). SEM micrographs of silk sericin at 2 μm scale bar are shown in Fig. 1. Results of SEM indicated that the size of the of silk sericin particles is approximately 102.5 nm.

GC-MS analysis of *Aloe vera* gel

A total of seventeen compounds were detected in *Aloe vera* gel by GC-MS analysis (Table 1). Five major compounds (2,4:3,5:6,7-Tri-O-benzylidene-1-deoxy-d-gulo-heptitol, stannane bis diphenyl, isopropyl myristate, 9-Octadecenoic acid and 10-Octadecenoic acid) identified in *Aloe vera* gel. Their molecular formula, molecular weight (MW), retention time (RT) and peak area (%) are presented in Table 2. Detail of major and minor compounds (Tables 1 and 2) detected through GC-MS analysis of *Aloe vera* gel will be helpful in future wound healing studies and they may be utilized individually or in combinations for preparing more effective gel formulations to treat chronic wounds.

Assessment of wound contraction

Healing area of wounds in treatment and control groups at day 11 is presented in Fig. 2 and at different days as percent wound contraction in Fig. 3.

Percent wound contraction at various days

Overall, there was significant difference in percent wound contraction between the treatment and control groups at day 3 ($F_{5,30} = 3.391$; $P = 0.015$), day 7 ($F_{5,30} = 7.561$; $P < 0.001$) and day 11 ($F_{5,30} = 29.19$; $P < 0.01$). There is a non-significant variation in

Table 1 List of major and minor compounds detected through the GC-MS analysis of *Aloe vera* gel.

	Compound name	Molecular formula	Molecular weight
1	2,4:3,5:6,7-Tri-O-benzylidene-1-deoxy-d-gluco-d-gulo-heptitol	C ₂₈ H ₂₈ O ₆	460
2	Glycine	C ₃₆ H ₆₉ NO ₆ Si ₃	695
3	Di-1,3-xylyl-24-crown-6, 5,5'-dimethyl-2,2'-bis(2-propenyloxy)	C ₃₂ H ₄₄ O ₈	556
4	Decyl .alpha.-d-galactoside, 2,4,6-detrioxy-3-O-benzyl-4,6-S-dibenzylthio	C ₃₇ H ₅₀ O ₃ S ₂	606
5	1,5- Anhydro-2,3-dibenzoyl-4,6-O-dibenzyl-d-glutitol	C ₃₄ H ₃₂ O ₇	552
6	Colchicine	C ₃₁ H ₃₁ NO ₇	529
7	Stannane, bis (pentafluorophenyl) diphenyl	C ₂₄ H ₁₀ F ₁₀ Sn	608
8	Inositol	C ₂₄ H ₆₀ O ₆ Si ₆	612
9	Galactonic acid	C ₂₄ H ₆₀ O ₇ Si ₆	628
10	Myo-Inositol	C ₂₄ H ₆₀ O ₆ Si ₆	612
11	Isopropyl Myristate	C ₁₇ H ₃₄ O ₂	270
12	9-Octadecenoic acid	C ₂₁ H ₃₈ O ₄	354
13	Dodecanoic acid	C ₁₅ H ₃₀ O ₂	242
14	Hexadecanoic acid, methyl ester	C ₁₇ H ₃₄ O ₂	270
15	10-Octadecenoic acid	C ₁₉ H ₃₆ O ₂	296
16	Pentadecanoic acid, 14-methyl-, methyl ester	C ₁₇ H ₃₄ O ₂	270
17	12-Octadecenoic acid, methyl ester	C ₁₉ H ₃₆ O ₂	296

Table 2 List of five major compounds with their retention time (RT) and peak area (%) detected through the GC-MS study of *Aloe vera* gel.

No	RT	Name of the compound	Molecular formula	Molecular weight	Peak area (%)
1	13.47	2,4:3,5:6,7-Tri-O-benzylidene-1-deoxy-d-gluco-d-gulo-heptitol	C ₂₈ H ₂₈ O ₆	460	10.83
2	13.443	Stannane, bis (pentafluorophenyl) diphenyl.	C ₂₄ H ₁₀ F ₁₀ Sn	608	10.77
3	17.879	Isopropyl Myristate	C ₁₇ H ₃₄ O ₂	270	15.98
4	18.894	9-Octadecenoic acid	C ₂₁ H ₃₈ O ₄	354	23.90
5	20.531	10-Octadecenoic acid	C ₁₉ H ₃₆ O ₂	296	38.52

percent wound contraction between T1 (5% sericin) and C1 (positive control; polyfax) ($P > 0.05$ ANOVA) at day 3. However, there was a significant difference in percent wound contraction on day 3 between T3 (5% fibroin) and C1 (positive control; polyfax) ($P = 0.043$ ANOVA).

At day 7 results of Tukey's test indicated that group C1 (positive control; polyfax) differs non-significantly from T1 (5% sericin) ($P > 0.05$ ANOVA) and T2 (5% sericin and 5% *Aloe vera*) ($P > 0.05$ ANOVA). On the other hand, there was a significant difference between T3 (5% fibroin) and C1 (positive control; polyfax) ($P = 0.037$). At day 11 results of Tukey's test showed that group C1 (positive control; polyfax) differs significantly from T3 (5% fibroin) ($P = 0.013$ ANOVA) and T4 (5% fibroin and 5% *Aloe vera* gel) ($P < 0.01$ ANOVA) in percent wound contraction (Fig. 3). However, the group C1 (positive control; polyfax) differs non-significantly from T1 (5% sericin) ($P > 0.05$ ANOVA) and T2 (5% sericin and 5% *Aloe vera*) ($P > 0.05$ ANOVA).

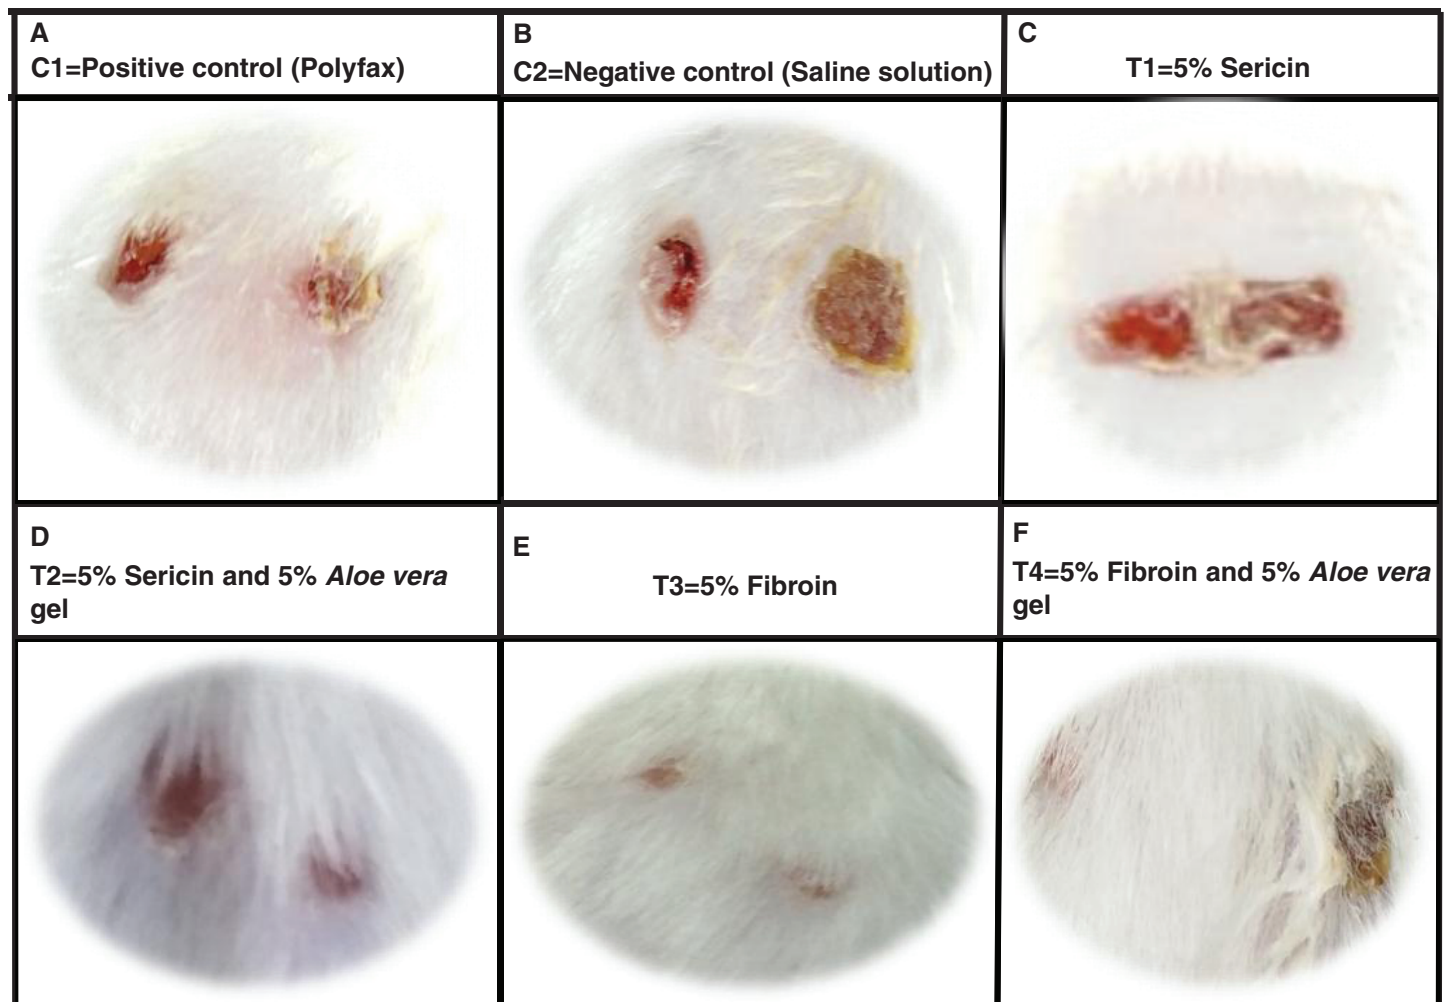


Figure 2 Wound healing process in different treatment groups at post wounding day 11. (A) C1 = Positive control (Polyfax); (B) C2 = Negative control (Saline solution); (C) T1 = 5% Sericin; (D) T2 = 5% Sericin and 5% *Aloe vera* gel; (E) T3 = 5% Fibroin; (F) T4 = 5% Fibroin and 5% *Aloe vera* gel. [Full-size !\[\]\(fcc3264021d438d9732560e78099f674_img.jpg\) DOI: 10.7717/peerj.10232/fig-2](https://doi.org/10.7717/peerj.10232/fig-2)

Histological analysis

Images of wound size in different treatment and control groups at post wounding day 10 is shown in Fig. 4. Best histological results were observed in group T4 (5% fibroin and 5% *Aloe vera* gel) in which the formation of the new epidermis was initiated and dermis with blood vessels and hair follicles were observed at post wounding day 10. However, histological results from group C1 (positive control; polyfax) showed the formation of collagen fibers and formation of thin epithelium and dermis at post wounding day 10. Healing of wound was incomplete until day 10 in positive control. In the group C2 (negative control; saline solution) there were inflammatory cells and adipose tissues at post wounding day 10.

Histological examination of wounded tissues from group T1 (5% sericin) showed the formation of the new epithelial layer. The wound was not completely epithelialized till day 10 and inflammatory cells were also observed. The histology of wound at 100X of

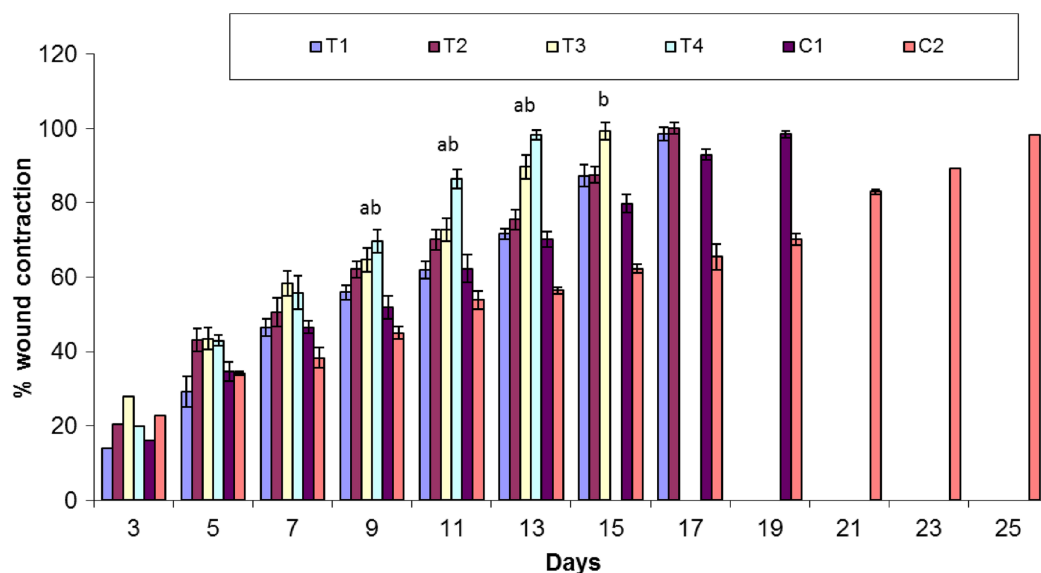


Figure 3 Comparison of percent wound contraction between treatment and control groups. Keys: C1 = Positive control (Polyfax); C2 = Negative control (Saline solution); T1 = 5% Sericin; T2 = 5% Sericin and 5% *Aloe vera* gel; T3 = 5% Fibroin; T4 = 5% Fibroin and 5% *Aloe vera* gel. 'a' indicates the significance difference between C2 and T3, 'b' indicates the significance difference between C2 and T4. Each bar represents the mean values and SEM of six replicates. Statistical icons: a, b = $p \leq 0.05$.

Full-size DOI: 10.7717/peerj.10232/fig-3

group T2 (i.e., 5% sericin and 5% *Aloe vera* gel) showed adipose tissues and new epithelium and formation of new blood vessels and dermis at day 10. The histology of wound from group T3 (5% fibroin) showed an uneven epidermal surface. However, the epidermal surface became even and no ulceration was observed on day 10 (Fig. 4).

DISCUSSION

In the present study, the potential of silk-based formulations to accelerate the wound healing process in diabetic mice was investigated. The results of this study indicated that silk sericin and fibroin when blended with *Aloe vera* gel quicken the healing process without causing any allergic reactions.

The wounds treated with 5% silk fibroin and 5% *Aloe vera* gel showed 85% healing in 11 days, however; wounds treated with 5% silk sericin and 5% *Aloe vera* gel showed 85% healing in 15 days. The results of wound healing treated with 5% silk sericin and 5% *Aloe vera* gel are comparable with findings of *Aramwit & Sangcakul (2007)* that 8% sericin cream significantly reduced wound healing time. Conversely, wounds treated with cream base healed in 15 days. Moreover, *Lamboni et al. (2015)* also reported that the incorporation of silk sericin in wound healing materials forms an exceptional biomaterial that stimulates re-epithelialization by improving the rate of migration, adhesion, growth of keratinocytes, fibroblasts and increased production of collagen at the wound site. In a clinical trial, (*Aramwit et al., 2013*) utilized 8% sericin combined with silver sulfadiazine cream (standard antibiotic cream) to treat open wounds caused by second-degree burns. Outcomes of the study showed that the average healing time of wounds was

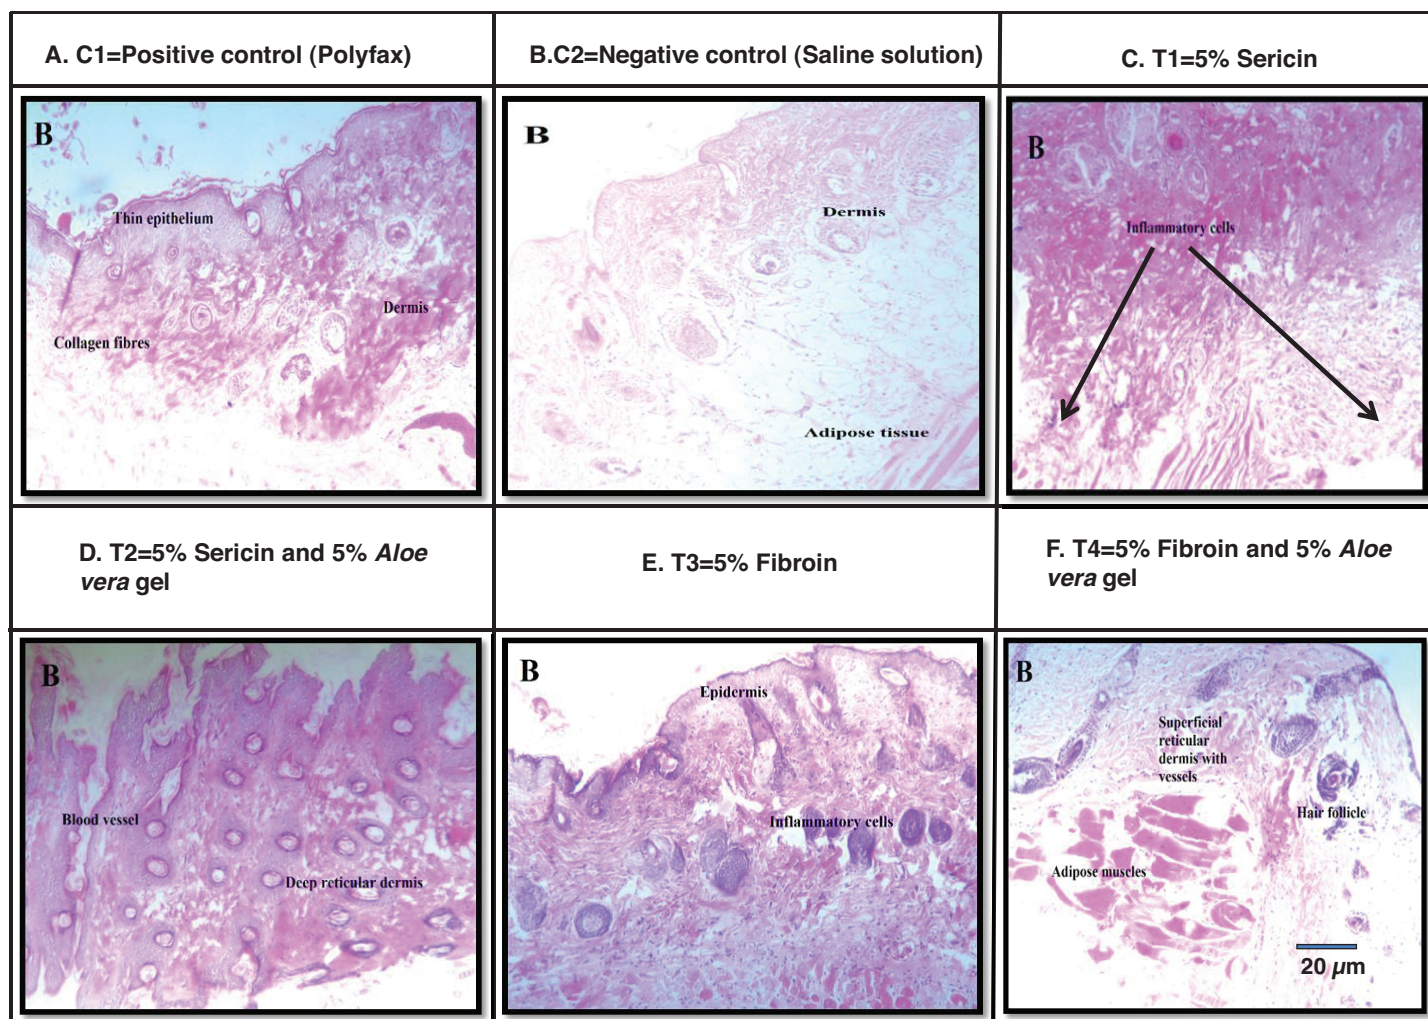


Figure 4 H & E staining showing the histological changes in diabetic mice skin at post-wounding day 10 in different treatment groups. Magnifications of 10X. Scale bar = 100 µm. (A) C1 = Positive control (Polyfax); (B) C2 = Negative control (Saline solution); (C) T1 = 5% Sericin; (D) T2 = 5% Sericin and 5% *Aloe vera* gel; (E) T3 = 5% Fibroin; (F) T4 = 5% Fibroin and 5% *Aloe vera* gel.

Full-size  DOI: 10.7717/peerj.10232/fig-4

significantly shorter in the treatment group compared to the control group (silver sulfadiazine without sericin).

Silk based films are considered safe and non-immunogenic biomaterial. The application of silk-based formulation on the skin does not affect serum profile since silk biofilm possess admirable biocompatibility with skin tissues. As it is infection-resistant in nature, it is regarded as an innovative wound coagulant biomaterial (Padol *et al.*, 2011). The current study also indicated that silk proteins (sericin and fibroin) based formulations do not cause any skin irritation, infection, or allergy when applied topically on wounds of diabetic mice.

Kanokpanont *et al.* (2013) created a silk fibroin based bi-layered wound dressing. Silk fibroin woven fabric coated with wax was taken as a non-adhesive layer whereas the sponge composed of silk sericin and glutaraldehyde-cross linked silk fibroin/gelatin was

fabricated as a bioactive layer. Treatment of wounds with bi-layered wound dressings exhibited the greater potential of wound reduction, increased epithelialization, and collagen formation when compared with clinically available wound dressings. Hence this bi-layered wound dressing is considered as an excellent candidate for healing full-thickness skin wounds. Similarly, in another experiment [Baygar \(2020\)](#) investigated the synergistic effect of propolis and biogenic metallic nanoparticles in combination with silk sutures for biomedical use. It was observed that silk sutures coated with propolis and biogenic AgNPs showed potent antibacterial potential besides providing wound healing activity and biocompatibility. In the present study, sericin and fibroin were applied individually as well as in combination with *Aloe vera* gel on excision wounds in diabetic mice. The results indicated that 5% fibroin when mixed with 5% *Aloe vera* gel showed the best results among all treatment groups. Healing time till 85% wound contraction was reduced as compared to the control group (polyfax) 15–17 days. These findings suggest that silk can be amalgamated with other natural products like plant extracts to make it biogenic and to improve its medicinal properties.

Aloe vera is a medicinal plant that is widely being explored by scientists for its natural healing ability for skin and other delicate tissues ([Jadhav et al., 2020](#)). Earlier studies showed that one or more components of *Aloe vera* stimulate wound healing in different animal models ([Gallagher & Gray, 2003](#)). [Chithra, Sajithlal & Chandrakasan \(1998\)](#) analyzed the effects of *Aloe vera* gel on full thickness wounds in diabetic rats. Their results revealed that treatment with *Aloe vera* gel speeds up the wound healing process by increasing the rate of collagen synthesis, affecting fibroplasia and wound size reduction. In another study, [Maenthaisong et al. \(2007\)](#) evaluated the effectiveness of *Aloe vera* in burn wounds. *Aloe vera* was observed to increase the rate of re-epithelialization and reduce the wound healing period for burn wounds. The results of the current research have also showed that the treatment groups in which silk protein (fibroin) was combined with *Aloe vera* gel showed greater wound healing potential as compared to a positive control (polyfax). This combination of silk and plant extract was also observed to be most biocompatible as compared to other treatment groups because no inflammation or ulceration was observed on the skin of diabetic mice during the experiment.

CONCLUSION

The results of this study suggests that silk based formulations can be utilized in wound healing materials because they are biocompatible, non-immunogenic and reduce wound healing time. This potential of silk-based formulations prepared in combination with *Aloe vera* gel has not previously been explored. Although the current research demonstrated the potential of silk derived formulations for wound healing in diabetic mice, the underlying molecular factors and events influencing wound healing are yet to be explored. Still, further studies need to be conducted to pinpoint how silk proteins influence the molecular events involved in the wound healing process. Improving wound healing treatments will improve the quality of life of diabetic patients suffering from chronic wounds along with a reduction in their health care costs.

ADDITIONAL INFORMATION AND DECLARATIONS

Funding

This work was supported by Higher Education Commission, Pakistan Technology Development Fund (No.TDF03-047). The funders had no role in study design, data collection and analysis, decision to publish, or preparation of the manuscript.

Grant Disclosures

The following grant information was disclosed by the authors:

Higher Education Commission, Pakistan Technology Development Fund: TDF03-047.

Competing Interests

The authors declare that they have no competing interests.

Author Contributions

- Muniba Tariq conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Hafiz Muhammad Tahir conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Samima Asad Butt conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Shaukat Ali conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Asma Bashir Ahmad conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Chand Raza conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Muhammad Summer conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Ali Hassan conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.
- Junaid Nadeem conceived and designed the experiments, performed the experiments, analyzed the data, prepared figures and/or tables, authored or reviewed drafts of the paper, and approved the final draft.

Animal Ethics

The following information was supplied relating to ethical approvals (i.e., approving body and any reference numbers):

The Institutional Bioethics Committee at Government College University Lahore approved this research (No. GCU/IIB/21 dated: 08-01-2019).

Data Availability

The following information was supplied regarding data availability:

The raw calculations of percent wound contraction in all groups are available in a [Supplemental File](#).

Supplemental Information

Supplemental information for this article can be found online at <http://dx.doi.org/10.7717/peerj.10232#supplemental-information>.

REFERENCES

- Ahmadi S, Ebrahimi SS, Oryan S, Rafieenia F. 2012.** Blockades of ATP-sensitive potassium channels and L-type calcium channels improve analgesic effect of morphine in alloxan-induced diabetic mice. *Pathophysiology* **19**(3):171–177 DOI [10.1016/j.pathophys.2012.04.007](https://doi.org/10.1016/j.pathophys.2012.04.007).
- Alberti KGMM, Zimmet PZ. 1998.** Definition, diagnosis and classification of diabetes mellitus and its complications—part 1: diagnosis and classification of diabetes mellitus. Provisional report of a WHO consultation. *Diabetic Medicine* **15**(7):539–553 DOI [10.1002/\(SICI\)1096-9136\(199807\)15:7<539::AID-DIA668>3.0.CO;2-S](https://doi.org/10.1002/(SICI)1096-9136(199807)15:7<539::AID-DIA668>3.0.CO;2-S).
- Ali S, Awan Z, Mumtaz S, Shakir HA, Ahmad F, Tahir HM, Ulhaq M. 2020a.** Cardiac toxicity of heavy metals (cadmium and mercury) and pharmacological intervention by vitamin C in rabbits. *Environmental Science and Pollution Research* **27**(23):29266–29279 DOI [10.1007/s11356-020-09011-9](https://doi.org/10.1007/s11356-020-09011-9).
- Ali S, Ejaz M, Dar KK, Nasreen N, Ashraf N, Gillani SF, Shafi N, Safeer S, Khan MA, Andleeb S, Mughal TA. 2020b.** Evaluation of chemopreventive and chemotherapeutic effect of *Artemisia vulgaris* against diethylnitrosamine induced hepatocellular carcinogenesis in Balb C mice. *Brazilian Journal of Biology* **80**(3):489–496 DOI [10.1590/1519-6984.185979](https://doi.org/10.1590/1519-6984.185979).
- Ali S, Hussain S, Khan R, Mumtaz S, Ashraf N, Andleeb S, Shakir HA, Tahir HM, Khan MKA, Ulhaq M. 2019.** Renal toxicity of heavy metals (cadmium and mercury) and their amelioration with ascorbic acid in rabbits. *Environmental Science and Pollution Research* **26**(4):3909–3920 DOI [10.1007/s11356-018-3819-8](https://doi.org/10.1007/s11356-018-3819-8).
- Altman GH, Diaz F, Jakuba C, Calabro T, Horan RL, Chen J, Lu H, Richmond J, Kaplan DL. 2003.** Silk-based biomaterials. *Biomaterials* **24**(3):401–416 DOI [10.1016/S0142-9612\(02\)00353-8](https://doi.org/10.1016/S0142-9612(02)00353-8).
- Ara C, Asmatullah, Butt N, Ali S, Batool F, Shakir HA, Arshad A. 2020.** Abnormal steroidogenesis, oxidative stress and reprotoxicity following prepubertal exposure to butyl paraben in mice and protective effect of *Curcuma longa*. *Environmental Science and Pollution Research*. Epub ahead of print 28 September 2020 DOI [10.1007/s11356-020-10819-8](https://doi.org/10.1007/s11356-020-10819-8).
- Aramwit P, Sangcakul A. 2007.** The effects of sericin cream on wound healing in rats. *Bioscience, Biotechnology and Biochemistry* **71**(10):2473–2477 DOI [10.1271/bbb.70243](https://doi.org/10.1271/bbb.70243).

- Aramwit P, Siritientong T, Srichana T. 2012.** Potential applications of silk sericin, a natural protein from textile industry by-products. *Waste Management & Research* **30(3)**:217–224 DOI [10.1177/0734242X11404733](https://doi.org/10.1177/0734242X11404733).
- Aramwit P, Palapinyo S, Srichana T, Chottanapund S, Muangman P. 2013.** Silk sericin ameliorates wound healing and its clinical efficacy in burn wounds. *Archives of Dermatological Research* **305(7)**:585–594.
- Atlas D. 2015.** *International diabetes federation: IDF, Diabetes Atlas*. Seventh Edition. Brussels: Scientific Research Publishing (SCIRP).
- Baygar T. 2020.** Characterization of silk sutures coated with propolis and biogenic silver nanoparticles (AgNPs); an eco-friendly solution with wound healing potential against surgical site infections (SSIs). *Turkish Journal of Medical Sciences* **50(1)**:258–266.
- Bouzhaya S, Amri M, Homblé F. 2020.** Improvement of diabetes symptoms and complications by an aqueous extract of *Linum usitatissimum* (L.) seeds in alloxan-induced diabetic mice. *Journal of Medicinal Food* 1–6 DOI [10.1089/jmf.2019.0205](https://doi.org/10.1089/jmf.2019.0205).
- Cassinelli C, Cascardo G, Morra M, Draghi L, Motta A, Catapano G. 2006.** Physical-chemical and biological characterization of silk fibroin-coated porous membranes for medical applications. *International Journal of Artificial Organs* **29(9)**:881–892.
- Chen T, Gao J, Xiang P, Chen Y, Ji J, Xie P, Wu H, Xiao W, Wei Y, Wang S, Lan L. 2015.** Protective effect of platycodin D on liver injury in alloxan-induced diabetic mice via regulation of Treg/Th17 balance. *International Immunopharmacology* **26(2)**:338–348 DOI [10.1016/j.intimp.2015.04.001](https://doi.org/10.1016/j.intimp.2015.04.001).
- Chithra P, Sajithlal GB, Chandrakasan G. 1998.** Influence of *Aloe vera* on the healing of dermal wounds in diabetic rats. *Journal of Ethnopharmacology* **59(3)**:195–201 DOI [10.1016/S0378-8741\(97\)00124-4](https://doi.org/10.1016/S0378-8741(97)00124-4).
- Chouhan D, Mandal BB. 2020.** Silk biomaterials in wound healing and skin regeneration therapeutics: from bench to bedside. *Acta Biomaterialia* **103**:24–51 DOI [10.1016/j.actbio.2019.11.050](https://doi.org/10.1016/j.actbio.2019.11.050).
- Dar KK, Ali S, Ejaz M, Nasreen S, Ashraf N, Gillani SF, Shafi N, Safer S, Khan MA4, Andleeb S, Mughal TA. 2019.** *In vivo* induction of hepatocellular carcinoma by diethylnitrosoamine and pharmacological intervention in balb c mice using *Bergeniaciolata* extracts. *Brazilian Journal of Biology* **79(4)**:629–638 DOI [10.1590/1519-6984.186565](https://doi.org/10.1590/1519-6984.186565).
- Das S, Baker AB. 2016.** Biomaterials and nanotherapeutics for enhancing skin wound healing. *Frontiers in Bioengineering and Biotechnology* **4**:82.
- Dehghani S, Dalirfardouei R, Jafari Najaf Abadi MH, Ebrahimi Nik M, Jaafari MR, Mahdipour E. 2020.** Topical application of curcumin regulates the angiogenesis in diabetic—impaired cutaneous wound. *Cell Biochemistry and Function* **38(5)**:558–566 DOI [10.1002/cbf.3500](https://doi.org/10.1002/cbf.3500).
- Dra LA, Sellami S, Rais H, Aziz F, Aghraz A, Bekkouche K, Markouk M, Larhsini M. 2019.** Antidiabetic potential of *Caralluma europaea* against alloxan-induced diabetes in mice. *Saudi Journal of Biological Sciences* **26(6)**:1171–1178 DOI [10.1016/j.sjbs.2018.05.028](https://doi.org/10.1016/j.sjbs.2018.05.028).
- El-Fakharany EM, Abu-Elreesh GM, Kamoun EA, Zaki S, Abd-E.L.-Haleem DA. 2020.** In vitro assessment of the bioactivities of sericin protein extracted from a bacterial silk-like biopolymer. *RSC Advances* **10(9)**:5098–5107 DOI [10.1039/C9RA09419A](https://doi.org/10.1039/C9RA09419A).
- Elahi E, Ali S, Tahir HM, Mushtaq R, Bhatti MF. 2020.** Sericin and fibroin nanoparticles—natural product for cancer therapy: a comprehensive review. *International Journal of Polymeric Materials and Polymeric Biomaterials* **509**:1–14 DOI [10.1080/00914037.2019.1706515](https://doi.org/10.1080/00914037.2019.1706515).

- Ersel M, Uyanikgil Y, Akarca FK, Ozcete E, Altunci YA, Karabey F, Cavusoglu T, Meral A, Yigitturk G, Cetin EO. 2016. Effects of silk sericin on incision wound healing in a dorsal skin flap wound healing rat model. *Medical Science Monitor: International Medical Journal of Experimental and Clinical Research* 22:1064.
- Falanga V. 2005. Wound healing and its impairment in the diabetic foot. *Lancet* 366(9498):1736–1743 DOI 10.1016/S0140-6736(05)67700-8.
- Farman N, Palacios-Ramirez R, Sbeih M, Behar-Cohen F, Aractingi S, Jaisser F. 2020. Cutaneous wound healing in diabetic mice is improved by topical mineralocorticoid receptor blockade. *Journal of Investigative Dermatology* 140(1):223–234 DOI 10.1016/j.jid.2019.04.030.
- Farokhi M, Mottaghitalab F, Fatahi Y, Khademhosseini A, Kaplan DL. 2018. Overview of silk fibroin use in wound dressings. *Trends in Biotechnology* 36(9):907–922 DOI 10.1016/j.tibtech.2018.04.004.
- Fini M, Motta A, Torricelli P, Giavaresi G, Aldini NN, Tschon M, Giardino R, Migliaresi C. 2005. The healing of confined critical size cancellous defects in the presence of silk fibroin hydrogel. *Biomaterials* 26(17):3527–3536 DOI 10.1016/j.biomaterials.2004.09.040.
- Gallagher J, Gray M. 2003. Is *Aloe vera* effective for healing chronic wounds? *Journal of Wound Ostomy and Continence Nursing* 30(2):68–71.
- Ha SW, Park YH, Hudson SM. 2003. Dissolution of *Bombyx mori* silk fibroin in the calcium nitrate tetrahydrate–methanol system and aspects of wet spinning of fibroin solution. *Biomacromolecules* 4(3):488–496 DOI 10.1021/bm0255948.
- Hussain S, Ali S, Mumtaz S, Shakir HA, Ahmad F, Tahir HM, Ulhaq M. 2020. Dose and duration-dependent toxicological evaluation of lead acetate in chicks. *Environmental Science and Pollution Research* 27(13):15149–15164 DOI 10.1007/s11356-020-08016-8.
- Jadhav AS, Patil OA, Kadam SV, Bhutkar MA. 2020. Review on *Aloe Vera* is used in medicinal plant. *Asian Journal of Research in Pharmaceutical Science* 10(1):26–30 DOI 10.5958/2231-5659.2020.00006.5.
- Jastrzebska K, Kucharczyk K, Florczak A, Dondajewska E, Mackiewicz A, Dams-Kozłowska H. 2015. Silk as an innovative biomaterial for cancer therapy. *Reports of Practical Oncology & Radiotherapy* 20(2):87–98 DOI 10.1016/j.rpor.2014.11.010.
- Ju HW, Lee OJ, Lee JM, Moon BM, Park HJ, Park YR, Lee MC, Kim SH, Chao JR, Ki CS, Park CH. 2016. Wound healing effect of electrospun silk fibroin nanomatrix in burn-model. *International Journal of Biological Macromolecules* 85:29–39.
- Kanokpanont S, Damrongsakkul S, Ratanavaraporn J, Aramwit P. 2013. An innovative bi-layered wound dressing made of silk and gelatin for accelerated wound healing. *International Journal of Pharmaceutics* 436(1–2):141–153 DOI 10.1016/j.ijpharm.2012.06.046.
- Khan R, Ali S, Mumtaz S, Andleeb S, Ulhaq M, Tahir HM, Khan MKA, Khan MA, Shakir HA. 2019. Toxicological effects of toxic metals (cadmium and mercury) on blood and the thyroid gland and pharmacological intervention by vitamin C in rabbits. *Environmental Science and Pollution Research* 26(16):16727–16741 DOI 10.1007/s11356-019-04886-9.
- Kundu B, Kurland NE, Bano S, Patra C, Engel FB, Yadavalli VK, Kundu SC. 2014. Silk proteins for biomedical applications: bioengineering perspectives. *Progress in Polymer Science* 39(2):251–267 DOI 10.1016/j.progpolymsci.2013.09.002.
- Lamboni L, Gauthier M, Yang G, Wang Q. 2015. Silk sericin: a versatile material for tissue engineering and drug delivery. *Biotechnology Advances* 33(8):1855–1867 DOI 10.1016/j.biotechadv.2015.10.014.

- Li Z, Song J, Zhang J, Hao K, Liu L, Wu B, Zheng X, Xiao B, Tong X, Dai F. 2020. Topical application of silk fibroin-based hydrogel in preventing hypertrophic scars. *Colloids and Surfaces B: Biointerfaces* 186:110735 DOI 10.1016/j.colsurfb.2019.110735.
- Lodhi S, Jain AP, Rai G, Yadav AK. 2016. Preliminary investigation for wound healing and anti-inflammatory effects of *Bambusa vulgaris* leaves in rats. *Journal of Ayurveda and Integrative Medicine* 7(1):14–22 DOI 10.1016/j.jaim.2015.07.001.
- MacIntosh AC, Kearns VR, Crawford A, Hatton PV. 2008. Skeletal tissue engineering using silk biomaterials. *Journal of Tissue Engineering and Regenerative Medicine* 2(2–3):71–80 DOI 10.1002/term.68.
- Maenthaisong R, Chaiyakunapruk N, Niruntraporn S, Kongkaew C. 2007. The efficacy of *Aloe vera* used for burn wound healing: a systematic review. *Burns* 33(6):713–718 DOI 10.1016/j.burns.2006.10.384.
- Martínez DCC, Zuluaga CL, Restrepo-Osorio A, Álvarez-López C. 2017. Characterization of sericin obtained from cocoons and silk yarns. *Procedia Engineering* 200:377–383 DOI 10.1016/j.proeng.2017.07.053.
- Martínez-Mora C, Mrowiec A, García-Vizcaíno EM, Alcaraz A, Cenis JL, Nicolás FJ. 2012. Fibroin and sericin from *Bombyx mori* silk stimulate cell migration through upregulation and phosphorylation of c-Jun. *PLOS ONE* 7(7):e42271 DOI 10.1371/journal.pone.0042271.
- Masood N, Ahmed R, Tariq M, Ahmed Z, Masoud MS, Ali I, Asghar R, Andleeb A, Hasan A. 2019. Silver nanoparticle impregnated chitosan-PEG hydrogel enhances wound healing in diabetes induced rabbits. *International Journal of Pharmaceutics* 559:23–36 DOI 10.1016/j.ijpharm.2019.01.019.
- Menke NB, Ward KR, Witten TM, Bonchev DG, Diegelmann RF. 2007. Impaired wound healing. *Clinics in Dermatology* 25(1):19–25.
- Min BM, Lee G, Kim SH, Nam YS, Lee TS, Park WH. 2004. Electrospinning of silk fibroin nanofibers and its effect on the adhesion and spreading of normal human keratinocytes and fibroblasts in vitro. *Biomaterials* 25(7–8):1289–1297 DOI 10.1016/j.biomaterials.2003.08.045.
- Mughal TA, Saleem MZ, Ali S, Anwar KK, Bashir MM, Babar M, Khan MA. 2019. Evaluation of hepatotoxicity of carbon tetrachloride and pharmacological intervention by vitamin E in balb c mice. *Pakistan Journal of Zoology* 51(2):755–761 DOI 10.17582/journal.pjz/2019.51.2.755.761.
- Mumtaz S, Ali S, Khan R, Andleeb S, Ulhaq M, Khan MA, Shakir HA. 2019. The protective role of ascorbic acid in the hepatotoxicity of cadmium and mercury in rabbits. *Environmental Science and Pollution Research* 26(14):14087–14096 DOI 10.1007/s11356-019-04620-5.
- Nishida A, Yamada M, Kanazawa T, Takashima Y, Ouchi K, Okada H. 2011. Sustained-release of protein from biodegradable sericin film, gel and sponge. *International Journal of Pharmaceutics* 407(1–2):44–52 DOI 10.1016/j.ijpharm.2011.01.006.
- Nithya V, Brinda P, Anand KV. 2011. Wound healing activity of *Leonotis nepetaefolia* r. br., in wistar albino rats. *Asian Journal of Pharmaceutical and Clinical Research* 4(2):23–26.
- Padol AR, Jayakumar K, Shridhar NB, Swamy NHD, Swamy MN, Mohan K. 2011. Safety evaluation of silk protein film (a novel wound healing agent) in terms of acute dermal toxicity, acute dermal irritation and skin sensitization. *Toxicology International* 18(1):17–21 DOI 10.4103/0971-6580.75847.
- Paquette D, Falanga V. 2002. Leg ulcers. *Clinics in Geriatric Medicine* 18(1):77–88 DOI 10.1016/S0749-0690(03)00035-1.

- Roh DH, Kang SY, Kim JY, Kwon YB, Kweon HY, Lee KG, Park YH, Baek RM, Heo CY, Choe J, Lee JH. 2006. Wound healing effect of silk fibroin/alginate-blended sponge in full thickness skin defect of rat. *Journal of Materials Science* 17(6):547–552.
- Schneider A, Wang XY, Kaplan DL, Garlick JA, Egles C. 2009. Biofunctionalized electrospun silk mats as a topical bioactive dressing for accelerated wound healing. *Acta Biomaterialia* 5(7):2570–2578 DOI 10.1016/j.actbio.2008.12.013.
- Shailendra SS, Das N. 2019. Silk fibroin in effective wound dressing: an overview. *International Journal of Advanced Research* 7(4):68–72.
- Siavashani AZ, Mohammadi J, Rottmar M, Senturk B, Nourmohammadi J, Sadeghi B, Huber L, Maniura-Weber K. 2020. Silk fibroin/sericin 3D sponges: the effect of sericin on structural and biological properties of fibroin. *International Journal of Biological Macromolecules* 153:317–326 DOI 10.1016/j.ijbiomac.2020.02.316.
- Spampinato SF, Caruso GI, De Pasquale R, Sortino MA, Merlo S. 2020. The treatment of impaired wound healing in diabetes: looking among old drugs. *Pharmaceuticals* 13(4):60 DOI 10.3390/ph13040060.
- Sugihara A, Sugiura K, Morita H, Ninagawa T, Tubouchi K, Tobe R, Izumiya M, Horio T, Abraham NG, Ikehara S. 2000. Promotive effects of a silk film on epidermal recovery from full-thickness skin wounds. *Proceedings of the Society for Experimental Biology and Medicine* 225(1):58–64 DOI 10.1046/j.1525-1373.2000.22507.x.
- Tahir HM, Jabeen J, Raza R, Ali S. 2019. Silk of spider and *Bombyx mori*: an overview. *Punjab University Journal of Zoology* 34(2):170–179 DOI 10.17582/journal.pujz/2019.34.2.221.229.
- Tahir HM, Saleem F, Ain Ali SQ, Summer M, Mushtaq R, Zahid MT, Liaqat I, Murtaza M. 2020. Synthesis of sericin-conjugated silver nanoparticles and their potential antimicrobial activity. *Journal of Basic Microbiology* 60(5):458–467.
- Vanitha M, Karthikeyan J. 2013. Evaluation of *Aloe vera* gel for its anti-inflammatory activity in diabetes mellitus using animal model system. *International Journal of Drug Development and Research* 5(1):305–309.
- Vasconcelos A, Pêgo AP, Henriques L, Lamghari M, Cavaco-Paulo A. 2010. Protein matrices for improved wound healing: elastase inhibition by a synthetic peptide model. *Biomacromolecules* 11(9):2213–2220 DOI 10.1021/bm100537b.
- Vepari C, Kaplan DL. 2007. Silk as a biomaterial. *Progress in Polymer Science* 32(8–9):991–1007 DOI 10.1016/j.progpolymsci.2007.05.013.
- Vollrath F, Porter D. 2006. Spider silk as a model biomaterial. *Applied Physics A* 82(2):205–212 DOI 10.1007/s00339-005-3437-4.
- Wang HY, Zhang YQ. 2013. Effect of regeneration of liquid silk fibroin on its structure and characterization. *Soft Matter* 9(1):138–145 DOI 10.1039/C2SM26945G.
- Yi B, Zhang H, Yu Z, Yuan H, Wang X, Zhang Y. 2018. Fabrication of high performance silk fibroin fibers via stable jet electrospinning for potential use in anisotropic tissue regeneration. *Journal of Materials Chemistry B* 6(23):3934–3945.
- Zhou CZ, Confalonieri F, Medina N, Zivanovic Y, Esnault C, Yang T, Jacquet M, Janin J, Duguet M, Perasso R, Li ZG. 2000. Fine organization of *Bombyx mori* fibroin heavy chain gene. *Nucleic Acids Research* 28(12):2413–2419 DOI 10.1093/nar/28.12.2413.